
वस्त्र रंजक सामग्री — डिस्पर्स रंजक, वैट
रंजक और पिगमेंट विस्थापन का मूल्यांकन
(पहला पुनरीक्षण)

**Textile Dyestuffs — Evaluation of
Disperse Dyes, Vat Dyes and
Pigments Migration**
(*First Revision*)

ICS 59.040; 71.040.50

© BIS 2023



भारतीय मानक ब्यूरो
BUREAU OF INDIAN STANDARDS
मानक भवन, 9 बहादुर शाह ज़फर मार्ग, नई दिल्ली - 110002
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG
NEW DELHI - 110002
www.bis.gov.in www.standardsbis.in

FOREWORD

This Indian Standard (First Revision) was adopted by the Bureau of Indian Standards, after the draft finalized by the Textile Speciality Chemicals and Dyestuffs Sectional Committee had been approved by the Textiles Division Council.

Vat dye, vat/disperse dye combinations and pigments are applied on cotton or polyester/cotton on a large scale by padding, drying and fixation. High speed continuous or semi-continuous methods require a sufficiently small particle size for optimum fixation of the dyes. However, small particle size increases the potential of undesirable migration during drying. In case drying conditions are not constant and/or uniform. Uneven migration may occur, causing shade variations during a run or shade differences between the face and back or between the side and centre of the fabric.

This standard was first published in 1997. The first revision of the standard has been made in the light of experience gained since its publication and to incorporate the following major changes:

- a) Title of the standard has been modified;
- b) Grade and purity of chemicals used have been specified; and
- c) References to Indian Standard have been updated.

The composition of the Committee responsible for the formulation of this standard is given in Annex A.

In reporting the results of a test or analysis made in accordance with this standard, if the final value, observed or calculated, is to be rounded off, it shall be done in accordance with IS 2 : 2022 'Rules for rounding off numerical values (*second revision*)'.

*Indian Standard***TEXTILE DYESTUFFS — EVALUATION OF DISPERSE DYES,
VAT DYES AND PIGMENTS MIGRATION***(First Revision)***1 SCOPE**

This standard describes a method for assessing the migration propensity (degree of migration) of the disperse dyes, vat dyes and pigments and which may also contain different types and amounts of migration inhibitors.

The test method maybe used to compare the migration propensity of dyes, and the effect on migration of different types of migration inhibitors, thickeners and electrolyte.

2 REFERENCES

The standards given below contain provisions which through reference in this text, constitute provision of this standard. At the time of publication, the editions indicated were valid. All standards are subject to revision and parties to agreements based on this standard are encouraged to investigate the possibility of applying the most recent edition of these standards:

<i>IS No.</i>	<i>Title</i>
IS 6359 : 2023	Method for conditioning of textiles (<i>first revision</i>)
IS/ISO 105-A02 : 1993	Textiles — Tests for colour fastness: Part A02 Grey scale for assessing change in colour

3 TERMINOLOGY

3.1 For the purpose of this standard the following definitions shall apply.

3.1.1 Dye — A colourant applied to or formed in a substrate, via the molecularly dispersed state, which exhibits some degree of permanence.

3.1.2 Pigment — A colourant in particulate form which is insoluble in a substrate, but which can be dispersed in the substrate to modify its colour.

3.1.3 Migration — Movement of a chemical, dye or pigment between fibres within a substrate or between substrates due to capillary forces.

4 PRINCIPLE

Fabric impregnated with dye alone or with dye and auxiliaries, is dried at room temperature. The fabric

is partially covered with a watch glass permitting differential drying to occur and therefore, migration to occur. Degree of migration is evaluated by visual examination, or by reflectance measurements of the covered and uncovered areas.

5 APPARATUS

5.1 Laboratory padder

5.2 Glass plate (60 cm × 35 cm)

5.3 Watch glass (9 cm) with 2.2 cm arch punch

5.4 Grey scale for colour change (*see* IS/ISO 105-A02)

5.5 Colourimeter or spectrophotometer

6 TEST SPECIMEN

6.1 Distilled water

6.2 Dyes in concentration desired

6.3 Auxiliaries in concentrations required

6.4 Fabric

A conditioned 15 cm × 30 cm swatch of substrate is desired (*see* IS 6359).

For disperse dyes, vat dyes and pigments, generally the preferred fabric is 65/35 polyester/cotton gabardine or heavy-twill fabric, heat set, bleached and mercerised. For soluble dyes with affinity to cellulose (reactive dyes) a bleached and mercerised 100 percent cotton gabardine or heavy twill fabric should be used. However, any other fabric intended for use on a continuous dye range may be chosen.

6.5 Wet pickup; whatever is convenient for the substrate under test but must be specified.

7 PROCEDURE

A 15 cm × 30 cm swatch of fabric is impregnated at room temperature in a bath containing dye (and auxiliaries), then padded to obtain desired wet pickup by adjusting the pressure at the nip of pad rolls. Generally the wet pickup is 60 percent, but may be adjusted to simulate wet pickup of a particular fabric to be run on a particular range.

Calculate wet pickup as weight gained by the substrate at ambient conditions after padding, from the following equation:

$$\text{Percentage wet pickup} = 100 \left(\frac{A}{B} - 1 \right)$$

where

A = weight after padding; and

B = weight before padding.

Immediately after padding, the fabric is placed on a flat glass plate. A 9 cm watch glass is placed on the fabric as shown in Fig. 1 and the fabric is dried at room temperature. The watch glass is removed and the degree of particulate migration is estimated by comparison of the dye concentration in the area of the fabric which was covered by the watch glass to the concentration in the rest of the fabric.

8 EVALUATION

8.1 Visual

8.1.1 Compare the depth of colour under the watch glass to the depth of colour of the rest of the fabric by references to the grey scale for colour change (see IS 768).

8.2 Reflectance Measurements

8.2.1 Determine the wavelength for measurement using a reference area of the untreated fabric. Make reflectance measurements on the area of fabric under the watch glass and on the rest of fabric using a spectrophotometer. Convert these values to K/S using the following equation:

$$\frac{K}{S} = (1-R)^2/2R$$

where

R is the reflectance factor at the wavelength of maximum absorption.

Calculate the migration percent to a nearest 1 percent from the following equation:

$$\text{Percent migration} = 100 [1 - (K/S)_a / (K/S)_b]$$

where

$(K/S)_a$ is the K/S value of the tested area (covered by watch glass); and

$(K/S)_b$ is the K/S value of the uncovered area of the fabric.

9 REPORT

The test report shall include the following:

- a) The substrate, the pad liquor composition including dyes, chemicals and auxiliaries and the wet pickup expressed as a percentage adjunct based on the untreated substrate;
- b) Room temperature, and relative humidity;
- c) Report the visual assessment on a scale of 1 to 5 by the grey scale for colour change:
 - Grade 5 — No migration
 - Grade 4 — Slight migration
 - Grade 3 — Medium migration
 - Grade 2 — Severe migration
 - Grade 1 — Very severe migration
- d) Report reflectance measurements as percentage particulate migration using the outer dyed area as a standard.

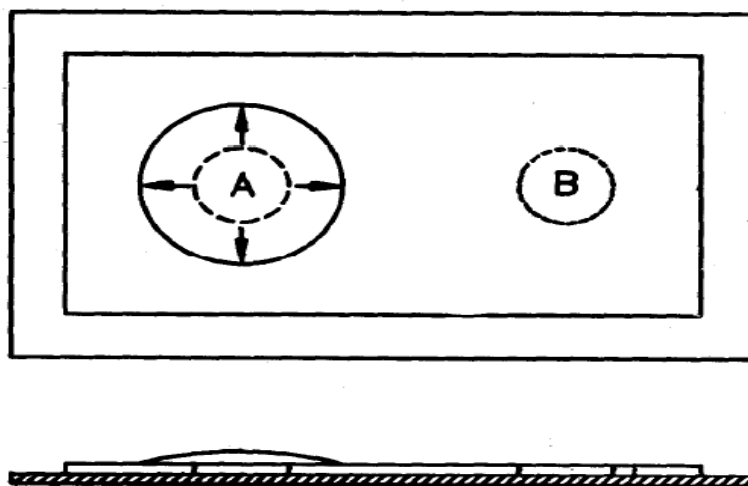


FIG. 1 LAYOUT OF APPARATUS FOR INDUCING COLOURANT MIGRATION

ANNEX A

(Foreword)

COMMITTEE COMPOSITION

Textile Speciality Chemicals and Dyestuffs Sectional Committee, TXD 07

<i>Organization</i>	<i>Representative(s)</i>
Department for Jute and Fibre Technology Institute of Jute Technology University of Calcutta, Kolkata	PROF A. K. SAMANTA (Chairperson)
Ahmedabad Textile Industry's Research Association, Ahmedabad	SHRIMATI DEEPALI PLAWAT SHRIMATI FAHIMUNNISA KHATIB (<i>Alternate</i>)
Ama Herbals Laboratories Pvt Ltd, Lucknow	SHRI Y. A. SHAH
Archroma India Pvt Limited, Mumbai	SHRI RAJESH RAMAMURTHY SHRIMATI PRACHI NARVEKAR (<i>Alternate</i>)
Atul Limited (Colors Business), Valsad	SHRI RAJARAM JAMDAD SHRI ARINDAM CHAKRABORTY (<i>Alternate</i>)
Bio Dyes India Pvt Ltd, Goa	DR BOSCO HENRIQUES
Central Coir Research Institute, Alappuzha	DR SHANMUGASUNDARAM O. L. DR S. RADHAKRISHNAN (<i>Alternate</i>)
Central Institute for Research on Cotton Technology, Mumbai	DR SUJATA SAXENA DR A. S. M. RAJA (<i>Alternate</i>)
Department for Jute and Fibre Technology Institute of Jute Technology University of Calcutta, Kolkata	DR D. DAS
Global Organic Textile Standard, (GOTS), Thane	SHRI RAHUL BHAIKAR MISS PRACHI GUPTA (<i>Alternate</i>)
Indian Jute Industries Research Association, Kolkata	DR S. K. CHAKRABARTI SHRI SANDIP BASU (<i>Alternate</i>)
Northern India Textile Research Association, Ghaziabad	DR M. S. PARMAR DR NIDHI SISODIA (<i>Alternate</i>)
Office of the Textile Commissioner, Mumbai	SHRI GAURAV GUPTA SHRI SANJAY CHARAK (<i>Alternate</i>)
SGS India Pvt Ltd, Mumbai	SHRI KARTHIKEYAN K. SHRI GAURAV SARASWAT (<i>Alternate</i>)
Shree Pushkar Chemicals & Fertilizers Ltd, Mumbai	DR N. N. MAHAPATRA
Textiles Committee, Mumbai	SHRI KARTIKEYA DHANDA SHRIMATI SHILPI CHAUHAN (<i>Alternate</i>)
The Arvind Mills Limited, Ahmedabad	SHRI RAJARSHI GHOSH SHRI UMASANKAR MAHAPATRA (<i>Alternate</i>)
The Bombay Textile Research Association, Mumbai	DR PADMA S. VANKAR SHRI M. P. SATHIANARAYANAN (<i>Alternate</i>)

<i>Organization</i>	<i>Representative(s)</i>
The South India Textile Research Association, Coimbatore	DR PRAKASH VASUDEVAN SHRI S. SIVAKUMAR (<i>Alternate</i>)
The Synthetic and Art Silk Mills Research Association, Mumbai	SHRIMATI (DR) MANISHA MATHUR SHRIMATI ASHWINI SUDAM (<i>Alternate</i>)
U P Textile Technology Institute, Kanpur	DR ARUN KUMAR PATRA DR SHUBHANKAR MAITY (<i>Alternate</i>)
Wool Research Association, Thane	SHRIMATI (DR) MRINAL CHOUDHARI
BIS Directorate General	SHRI J. K. GUPTA, SCIENTIST 'E'/DIRECTOR AND HEAD (TEXTILES) [REPRESENTING DIRECTOR GENERAL (<i>Ex-officio</i>)]

Member Secretary
SHRI HIMANSHU SHUKLA
SCIENTIST 'B'/JOINT DIRECTOR
(TEXTILES), BIS

Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 2016* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Head (Publication & Sales), BIS.

Review of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the website- www.bis.gov.in or www.standardsbis.in.

This Indian Standard has been developed from Doc No.: TXD 7 (21080).

Amendments Issued Since Publication

Amend No.	Date of Issue	Text Affected

BUREAU OF INDIAN STANDARDS

Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002

Telephones: 2323 0131, 2323 3375, 2323 9402

Website: www.bis.gov.in

Regional Offices:

	Telephones
Central : 601/A, Konnectus Tower -1, 6 th Floor, DMRC Building, Bhavbhuti Marg, New Delhi 110002	{ 2323 7617
Eastern : 8 th Floor, Plot No 7/7 & 7/8, CP Block, Sector V, Salt Lake, Kolkata, West Bengal 700091	{ 2367 0012 2320 9474
Northern : Plot No. 4-A, Sector 27-B, Madhya Marg, Chandigarh 160019	{ 265 9930
Southern : C.I.T. Campus, IV Cross Road, Taramani, Chennai 600113	{ 2254 1442 2254 1216
Western : Plot No. E-9, Road No.-8, MIDC, Andheri (East), Mumbai 400093	{ 2821 8093

Branches : AHMEDABAD. BENGALURU. BHOPAL. BHUBANESHWAR. CHANDIGARH. CHENNAI. COIMBATORE. DEHRADUN. DELHI. FARIDABAD. GHAZIABAD. GUWAHATI. HIMACHAL PRADESH. HUBLI. HYDERABAD. JAIPUR. JAMMU & KASHMIR. JAMSHEDPUR. KOCHI. KOLKATA. LUCKNOW. MADURAI. MUMBAI. NAGPUR. NOIDA. PANIPAT. PATNA. PUNE. RAIPUR. RAJKOT. SURAT. VISAKHAPATNAM.